

## PREPARATION AND CHARACTERIZATION OF HERBAL NANOFORMULATION CONTAINING *ANDROGRAPHIS PANICULATA* EXTRACT

A. Uma Devi <sup>\*1</sup> and Salma Khanam <sup>2</sup>

Department of Pharmacognosy <sup>1</sup>, Moulana College of Pharmacy, Angadippuram, Perinthalmanna, Malappuram - 679321, Kerala, India

Department of Pharmacognosy <sup>2</sup>, Al-Ameen College of Pharmacy, Bangalore - 560027, Karnataka, India.

**ABSTRACT:** This study aimed to investigate the preparation and characterization of polymeric nanoparticles containing extract of *Andrographis paniculata* using Eudragit S 100 polymer. The methanolic extract of aerial parts of *Andrographis paniculata* Nees (Acanthaceae) was prepared and standardized for andrographolide content using the High-Performance Liquid chromatography technique. Three formulations containing 50, 100 and 150 mg of extract were prepared by solvent displacement method. Parameters including drug: polymer ratio, stabilizer, solvent, and stirring speed were optimized. Characterization of the formulations was carried out using particle size analysis, PDI, DSC, X-RD, SEM techniques, entrapment efficiency and *in-vitro* drug release studies. The particle size of the nanoformulations was found to be within the range of 300-400 nm, with entrapment efficiency more than 75% and drug release more than 55% after 8 h. Aerial parts extract of *Andrographis paniculata* was embedded and dispersed in Eudragit S 100 polymer as smooth spherical nanoparticles which may prove to be a novel drug delivery system.

### Keywords:

*Andrographis paniculata* extract, Andrographolide, HPLC, Polymeric nanoparticles, Nano formulation, DSC, X-RD, SEM techniques

**INTRODUCTION:** Nanoparticles are sub- a nanosized colloidal structure composed of synthetic or semi-synthetic polymer with Size range of 10-1000 nm. The drug is dissolved, entrapped, encapsulated or attached to a nanoparticle matrix (carriers). The use of nanoparticles allows changing the pharmacokinetic properties of the drug without changing the active compound <sup>1</sup>. Novel drug delivery systems not only reduce the repeated administration to overcome non-compliance but also help to increase the therapeutic value by reducing toxicity and increasing the bioavailability.

Nano-sized drug delivery systems of herbal drugs have a potential future for enhancing the activity and overcoming problems associated with plant medicines. However, there are some limitations of these herbal extracts/plant actives like instability in highly acidic pH, liver metabolism, short half-life, solubility, etc. <sup>2</sup>.

<sup>3</sup> Various novel drug delivery systems such as microspheres, Nano suspension, Nanoemulsions, polymeric nanoparticles, etc., have been reported for herbal drugs <sup>4</sup>.

Various herbal novel formulations containing nanoparticles and phytosomes of drugs like *Silybum marianum*, *Ginkobiloba*, *Curcuma longa* have shown their potential as controlled and targeted drug delivery systems. The sustained-release formulations of *Boswellia serrata*, *Calendula officinalis*, *Commiphora wightii* and some Chinese drugs using nanotechnology have also been documented <sup>5, 6</sup>.

*Andrographis paniculata* Nees (Acanthaceae) commonly called Kalmegh is a well-known medicinal plant of Ayurveda with various pharmacological properties, has been used for treatment of various liver disorders

and jaundice. The major phytoconstituent of the plant are diterpene lactones including andrographolide, deoxyandrographolide, neoandrographolide, and andrographolide <sup>7</sup>. The ingredients are also reported to be unstable in extracts of gastrointestinal acidic and alkaline pH conditions with short biological half-life. Preparation of polymeric nanoparticles of andrographolide with improved physicochemical properties and consequently its bioavailability of drugs has been reported <sup>8</sup>.

Similarly, the preparation of Nanoformulation of the extract also may be beneficial. With this background the present study was proposed to encapsulate extract of *Andrographis paniculata* containing andrographolide and other ingredients in extract to overcome its disadvantages.

#### **MATERIALS AND METHODS:**

**Materials:** Dried aerial parts of *Andrographis paniculata* were taken from the Amrit Kesari, Bangalore, India and authenticated from National Ayurveda Dietetics Research Institute (NADRI), Bangalore. Voucher specimen no. SMPU/NADRI/ BNG/2013-2014/258. The drug was powdered and stored in polythene bags.

**Preparation of the Extract:** The air-dried powdered material (1 kg) of the sample was defatted by refluxing with petroleum ether (60° - 80°) for 8 h. The defatted powdered material of sample was subjected to Soxhlet extraction with methanol for 12 h. The extract was concentrated under reduced pressure on rotary evaporator to obtain the crude extract. The percentage yield was calculated with respect to air-dried drug. The extract was stored in an airtight container for further use.

**Estimation of Andrographolide content in the extract by HPLC:** The methanolic extract of Kalmegh was subjected to HPLC analysis for the estimation of andrographolide using reported method <sup>9</sup>.

**Instrument:** Shimadzu HPLC.

**Column:** C18 (250 mm × 4.6 mm).

**Mobile Phases:** Acetonitrile: 0.1% w/w Ortho- phosphoric acid in water (40: 60v/v).

**Flow Rate:** 1 ml/min.

**Injection Volume:** 100 µl

**λ max:** 223 nm

**Elution:** Binary gradient.

**Sample Preparation:** 100 mg of methanolic extract was dissolved in 10 ml of HPLC grade methanol with the help of sonication.

**Standard Preparation:** 5 mg of andrographolide was dissolved in 5 ml of HPLC grade methanol.

**Procedure:** 100 µl of, standard was injected and the peak area at Rt 4.7 was noted. 100 µl of sample was then injected and the peak area at Rt 4.7 was noted. The amount of andrographolide in the extract was calculated.

**Preparation of Nano Formulation:** The solvent displacement method was selected for the preparation of nanoformulation as polymeric nanoparticles using the methanolic extract of Kalmegh <sup>10, 11</sup>. The method was first standardized using placebo preparation. Nanoparticles were prepared by varying type, amount of solvent and stabilizer. Based on particle size and PDI analysis best possible combination of solvent, polymer and stabilizer was selected. The nanoparticles were prepared with 50, 100 and 150 mg of extract. For optimization of different parameters such as drug-polymer ratio, stirring speed, the concentration of stabilizer, and volume of aqueous phase, 4 sets of experiments with 9 formulations were carried out, and the prepared formulations were evaluated for particle size and PDI. In each set of experiments, only one formulation variable was changed at a time while the other parameters were kept same. The best formulation having range between 300-400 nm particle size and 0.1-0.7 PDI was selected for the study.

**Procedure:** The polymer Eudragit S 100 along with 50 mg, 100 mg, 150 mg of Kalmegh extract in the ratio of 1:4, 1:2, 1:1 were dissolved in 30 ml of ethanol which formed the organic phase. This organic phase was added at the rate of 2 ml/min under atmospheric pressure into an aqueous medium (50 ml) containing 1.5% Of polyvinyl alcohol as the stabilizer under 15000 rpm using Ultra Turrax homogenizer. After the addition of the organic phase, stirring was continued for 15 min at the same speed. After 30 min, the colloidal dispersion was subjected to mild stirring to remove ethanol. The milky colloidal suspension was formed. The batches were named F1, F2 and F3.

**Nanoparticle Characterization:** The nano-formulation was characterized by particle size, PDI, DSC, SEM, X-RD <sup>12-13</sup>.

**Particle Size Determination:** To analyze particle size, Samples were analyzed using Malvern Zetasizer S 90 UK which allows sample measurement in the range of 0.020-2000.00  $\mu\text{m}$ .

**Freeze Drying / Lyophilization of Nanoformulation:** Nano formulation F3 with 150 mg of extract was treated with 5% w/v of mannitol (1:5 ratio) and freeze-dried using Operon FBD-5503 lyophilizer. The freeze-dried free-flowing powder was subjected to characterization using DSC, SEM, and X-RD.

**Differential Scanning Calorimetry:** The extract and the formulation were subjected to DSC separately using a modulated DSC Instrument: SDT Q600 V20.9 at IISC, Bangalore.

**Scanning Electron Microscopy:** The formulation and the extract were subjected to microscopic examination (SEM) using Joel 840A scanning electron microscope for characterizing size and shape at IISC, Bangalore.

**X-ray Diffraction:** The extract and the formulation were subjected to X-RD study. Powder X-ray diffraction (PXRD) patterns were traced employing an X-ray diffractometer for the samples, using Cu K $\alpha$ 1- radiation at IISC, Bangalore.

**Drug Entrapment Efficiency:** The nanoparticle suspension (2 ml) was taken and cold Centrifuged at 10000 rpm for 30 min. The supernatant contains unentrapped drug and sediment contains the entrapped drug. The supernatant was analyzed by HPLC for free drugs. The Percentage drug entrapment was calculated using the straight-line equation from Standard calibration curve by direct method <sup>14</sup>.

Entrapment efficiency was calculated using the formula = (Mass of total drug taken - Mass of the drug in supernatant / Mass of total drug taken)  $\times$  100

**In-vitro Drug Release Study:** *In-vitro* drug release from the formulations was determined by using dialysis membrane (cellophane membrane, molecular weight cut off 10000-12000 Da, Hi-Media, India). The release study was performed in a phosphate buffer at different time intervals up to 8hrs.

**RESULTS AND DISCUSSION:** The methanolic extract was prepared and its yield was found to be 19.1%.

**Estimation of Andrographolide in Extract Content by HPLC:** Percentage of andrographolide was found to be 11.14%. The chromatograms of standard and extract were shown in Fig. 1 and 2.

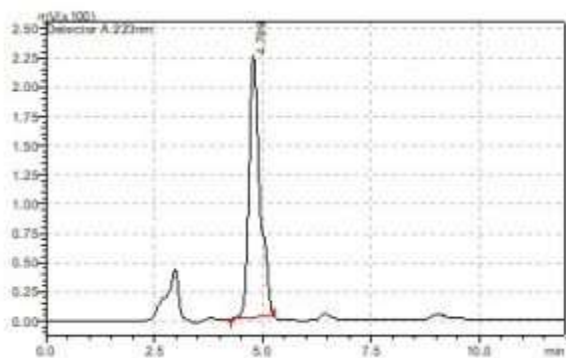


FIG. 1: HPLC CHROMATOGRAM OF ANDROGRAPHOLIDE

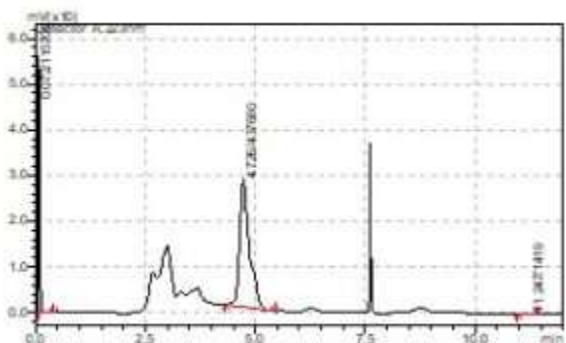


FIG. 2: CHROMATOGRAM OF KALMEG EXTRACT

**Preparation of Nanoformulation:** Optimized process parameters used for the preparation of nanoformulation are shown in **Table 3**.

**Particle Size:** The particle size and PDI of the nanoformulations are shown in graphs, are shown in **Fig. 3-5**. The particle size was within the limit of 300-400 nm, and PDI was less than 0.7.



FIG. 3: PARTICLE SIZE ANALYSIS OF NANOFORMULATION F1



FIG. 4: PARTICLE SIZE ANALYSIS OF NANOFORMULATION F2

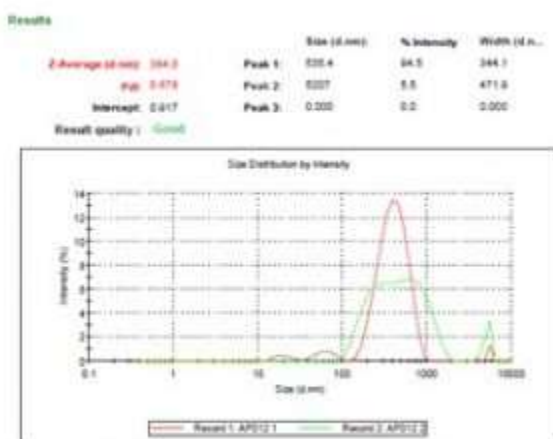


FIG. 5: PARTICLE SIZE ANALYSIS OF NANOFORMULATION F3

**Differential Scanning Calorimetry:** The DSC thermogram of Kalmegh extract exhibited a single endothermic sharp peak at 230 °C which may correspond to melting point. In the nanoformulation of extract with the Eudragit S100, an endothermic peak located at 181 °C was observed and the peak of Kalmegh extract (drug) disappeared completely. The disappearance of the drug endothermic peak in the nanoparticles suggested that Kalmegh extract might be embedded into Eudragit S100. The thermograms are shown in **Fig. 6** and **7**.

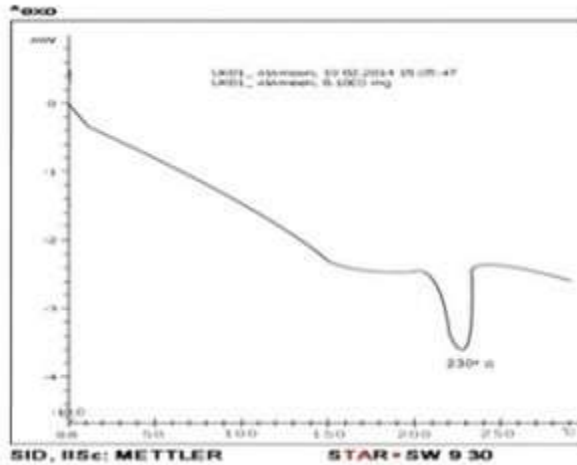


FIG. 6: DSC THERMOGRAM OF KALMEGH EXTRACT

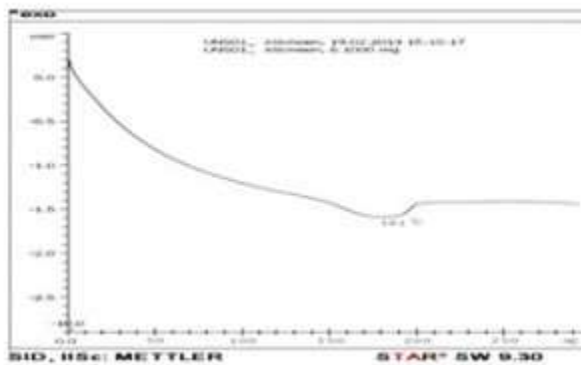


FIG. 7: DSC THERMOGRAM OF NANOFORMULATION

**Scanning Electron Microscopy:** The drug-loaded nanoparticles were found to be spherical with a smooth surface. The extract was found to have ruptured surfaces. The images are shown in **Fig. 8** and **9**.

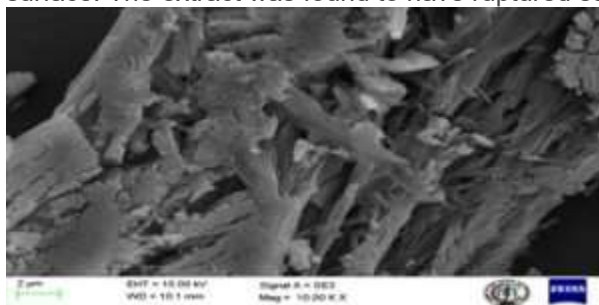


FIG. 8: SEM OF KALMEGH EXTRACT

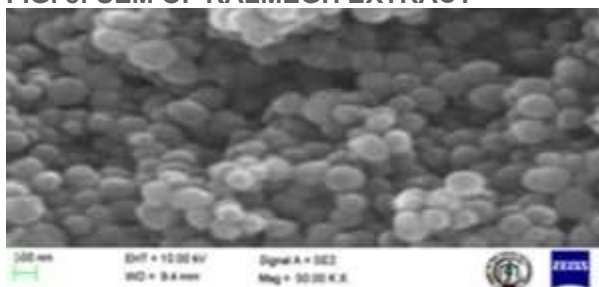
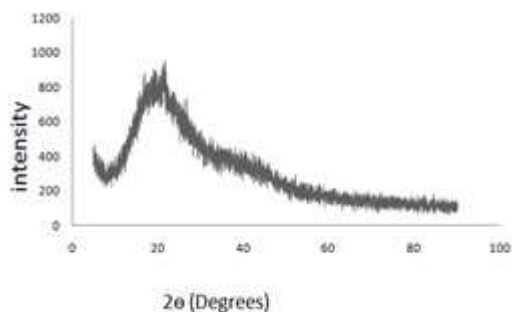
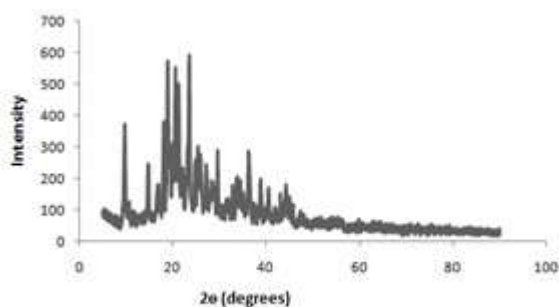


FIG. 9: SEM OF NANOPARTICLES OF NANOFORMULATION

**X-ray Diffraction:** The prominent peaks of Kalmegh extract were also seen at the same position in the nanoformulation with decreased intensity as shown in **Fig. 10** and **11**.



**FIG. 10: X-RAY DIFFRACTION PATTERN OF KALMEGH EXTRACT**



**FIG. 11: X-RAY DIFFRACTION PATTERN OF NANOPARTICLE DRY POWDER CONTAINING EUDRAGIT S 100, POLY VINYL ALCOHOL AND KALMEGH EXTRACT**

**Drug Entrapment Efficiency:** The drug entrapment efficiency for all the formulation is shown in **Table 4**. The formulation containing 50 mg with 1:4 drug-polymer ratio showed 91.8% of entrapment whereas formulation with 100 mg of extract with 1:2 drug-polymer ratio showed 80.43% of entrapment and formulation contain 150mg of extract with 1:1 drug-polymer ratio showed only 74.8% entrapment. These results are agreement with the literature, which documented that the efficiency increases with the increase in polymer concentration.

**In-vitro Drug Release Study:** Formulation 1 contain 50 mg of an extract with 1:4 Drug- Polymer ratio, and least particle size exhibited 64% of release after 8 h whereas the other two formulations showed 58% and 57% respectively. These results are in agreement with other reported findings <sup>15</sup>; lesser the particle size drug release is more.

**CONCLUSION:** Methanolic extract of aerial parts of *Andrographis paniculata* (Acanthaceae) commonly known as Kalmegh was embedded and displaced in Eudragit S 100 as smooth spherical nanoparticles with good entrapment and drug release. The formulation may be used as a novel drug delivery system.

**ACKNOWLEDGEMENT:** The author sincerely thanks Dr. Salma Khanam, M. Pharm, Ph.D., Al-Ameen College of Pharmacy, Bangalore for her constant support and valuable suggestions in completing this manuscript.

**AUTHORS CONTRIBUTION:** All the authors have contributed equally.

**CONFLICTS OF INTEREST:** Declare none

**REFERENCES:**



1. Subbaiya R, Shiyamala M, Revathi K, Pushpalatha R and Selvam MM: Biological synthesis of silver nanoparticles from *Nerium oleander* and its antibacterial and antioxidant property. International Journal of Current Microbiology and Applied Sciences 2014; 3(1): 83-87.
2. Fadli A, Nizam AG, Ibrahim A, Nurulnadiyah AK, Jiyauddin K and Samer AD: Formulation of tetracycline nanoemulsion. World Journal of Pharmaceutical Research 2015; 4(4): 134-44.
3. Krishnasis C, Arun S and Sundaram R: Nano-technology in herbal medicines: A review. International Journal of Herbal Medicine 2016; 4(3): 21-27.
4. P Heera and S Shanmugam: Nanoparticle characterization and application: an overview. International Journal of Current Microbiology and Applied Sci 2015; 4(8): 379-86.
5. Zhang XF, Liu ZG, Shen W and Sangiliyandi G: Silver Nanoparticles: Synthesis, characterization, properties, applications, and therapeutic approaches. International Journal of Molecular Sciences 2016; 17: 1534.
6. Gopi S, Amalraj A, Haponiuk J and Thomas S: Introduction of nanotechnology in herbal drugs and nutraceutical: a review. Journal of Nanomedicine & nr uoJ Biotherapeutic Discovery 2016; 6(2): 143.
7. Nyeem MA, Mannan MA, Nuruzzaman M, Kamrujjaman KM and Das SK: Indigenous king of bitter (*Andrographis paniculata*): A review. Journal of Medicinal Plants Studies 2017; 5(2): 318-24.
8. Raghavan R, Cheriyaundath S and Madassery J: Exploring the mechanisms of cytotoxic and anti-inflammatory property of andrographolide and its derivatives. Pharmacognosy Review 2018; 12: 56-65.
9. Sharma S and Sharma YP: Comparison of different extraction methods and HPLC method development for the quantification of andrographolide from *Andrographis paniculata* (Burm. f.) Wall. ex Nees. Annals of Phytomedicine 2018; 7(1): 119-30.
10. Tiruwa R: A review on nanoparticles – preparation and evaluation parameters. Indian Journal of Pharmaceutical and Biological Research 2015; 4(2): 27-31.